

FORMULATION OF THE HEAT CONDUCTION EQUATION FOR HETEROGENEOUS MEDIA WITH MULTIPLE SPATIAL SCALES USING REITERATED HOMOGENIZATION

Ernesto Iglesias Rodríguez

IGP Servicio Geológico de Cuba, Vía Blanca No. 1002, La Habana, CP 11000, Cuba
ernesto@igp.minem.cu

Manuel Ernani Cruz

UFRJ - Federal University of Rio de Janeiro, Department of Mechanical Engineering, Politécnica/COPPE, CT, CP 68503, Cidade Universitária, Rio de Janeiro, RJ, 21941-972, Brazil
manuel@mecanica.coppe.ufrj.br

Julián Bravo-Castillero

Raúl Guinovart-Díaz

Reinaldo Rodríguez-Ramos

Universidad de La Habana, Departamento de Matemática, Facultad de Matemática y Computación, L y San Lázaro, Vedado, La Habana, CP 10400, Cuba
jbravo@matcom.uh.cu, guino@matcom.uh.cu, reinaldo@matcom.uh.cu

Leslie Darien Pérez-Fernández

UFPel - Federal University of Pelotas, Department of Mathematics and Statistics, Institute of Physics and Mathematics, CP 354, Pelotas, RS, 96010-971, Brazil
leslie.fernandez@ufpel.edu.br

Abstract. *Heterogeneous media with multiple spatial scales are finding increased importance in engineering. An example might be a large scale, otherwise homogeneous medium filled with dispersed small-scale particles that form aggregate structures at an intermediate scale. The objective in this paper is to formulate the strong-form Fourier heat conduction equation for such media using the method of reiterated homogenization. The phases are assumed to have a perfect thermal contact at the interface. The ratio of two successive length scales of the medium is a constant small parameter ε . The method is an up-scaling procedure that writes the temperature field as an asymptotic multiple-scale expansion in powers of the small parameter ε . The technique leads to two pairs of local and homogenized equations, linked by effective coefficients. In this manner the medium behavior at the smallest scales is seen to affect the macroscale behavior, which is the main interest in engineering. To facilitate the physical understanding of the formulation, an analytical solution is obtained for the heat conduction equation in a functionally graded material (FGM). The approach presented here may serve as a basis for future efforts to numerically compute effective properties of heterogeneous media with multiple spatial scales.*

Keywords: *heat conduction, heterogeneous media, reiterated homogenization, formal asymptotic solution, FGM.*

1. INTRODUCTION

In some recent engineering applications it has become important to know the macroscopic behavior of heterogeneous materials in terms of several different microscopic levels. Reiterated homogenization is a mathematical technique for deriving the effective coefficients for such type of complex media. From the mathematical point of view, the homogenization process allows to transform problems involving systems of partial differential equations with rapidly oscillating coefficients in others, wherein the coefficients are not rapidly oscillating, and are the so-called effective coefficients. To demonstrate proximity between the solutions of the original and the homogenized problems is the key for the mathematical justification. Classical studies of the linear elliptic partial differential equation can be found, for instance, in Panasenko (2008) for two-scale media, and in Bensoussan *et al.* (1978) and Allaire and Briane (1996) for media with two or more spatial scales.

As an application-oriented study, the aim of this work is to, first, describe didactically the formal procedure of the reiterated homogenization method for the Fourier heat conduction equation with differentiable coefficients. Second, the formulation is employed to obtain the effective properties of a conductive functionally graded material – FGM (Mahamood

et al., 2012; Paulino *et al.*, 2009; Yin *et al.*, 2005) with periodic, rapidly oscillating, isotropic, and infinitely differentiable coefficients. The approach presented here may serve as a basis for future efforts to numerically compute effective properties of heterogeneous media with multiple spatial scales, and may be useful for the development of behavioral models to be embodied in a broader multi-material design method (Wargnier *et al.*, 2014).

Let Ω be a three-dimensional open connected bounded subset with a sufficiently smooth boundary $\partial\Omega$. The domain Ω extends over the spatial coordinate $\mathbf{x}$. Two structural levels are considered, such that ε denotes the small positive parameter that is the ratio of two successive length scales of the medium. Thus, the fast variables $\mathbf{y}$ and $\mathbf{z}$ are defined, $\mathbf{y} \equiv \mathbf{x}/\varepsilon$, $\mathbf{z} \equiv \mathbf{y}/\varepsilon = \mathbf{x}/\varepsilon^2$. The components of the conductivity tensor $k_{ij}^\varepsilon(\mathbf{x}) = k_{ij}(\mathbf{x}, \varepsilon) = k_{ij}(\mathbf{x}/\varepsilon, \mathbf{x}/\varepsilon^2) = k_{ij}(\mathbf{y}, \mathbf{z})$ are $Y \times Z$ -periodic differentiable functions.

The formalism of the reiterated homogenization method is here applied to the following family of boundary value problems depending on ε ,

$$\frac{\partial}{\partial x_i} \left(k_{ij}^\varepsilon \frac{\partial T^\varepsilon}{\partial x_j} \right) = f, \quad \text{in } \Omega, \quad (1)$$

$$T^\varepsilon = 0, \quad \text{on } \partial\Omega, \quad (2)$$

where $T^\varepsilon(\mathbf{x})$ is a scalar field, $\mathbf{K} = (k_{ij}^\varepsilon)$ is a symmetric and positive definite matrix-valued function, and $f(\mathbf{x}) \in C^\infty(\Omega)$. Physically, problem (1)-(2) may govern the temperature field T^ε set up by heat conduction in a medium with thermal conductivity k_{ij}^ε .

By applying the reiterated homogenization method, Eqs. (1)-(2) are transformed in

$$\hat{k}_{ij} \frac{\partial^2 T}{\partial x_i \partial x_j} = f, \quad \text{in } \Omega, \quad (3)$$

$$T = 0, \quad \text{on } \partial\Omega, \quad (4)$$

where $\hat{\mathbf{K}} = (\hat{k}_{ij})$ is a symmetric, positive definite matrix with constant entries. The new problem (3)-(4) is called the *homogenized problem*. The entries of $\hat{\mathbf{K}}$ are the *effective coefficients* which determine the macroscopic behavior of the heterogeneous medium.

2. HOMOGENIZATION: LOCAL AND HOMOGENIZED PROBLEMS, AND EFFECTIVE COEFFICIENTS

In this section, following Bensoussan *et al.* (1978) and Bakhvalov and Panasenko (1989), the reiterated homogenization method is applied to the problem (1)-(2). The following operators and notations are used in this section:

$$L_{p,q} = \frac{\partial}{\partial p_i} \left(k_{ij} \frac{\partial}{\partial q_j} \right),$$

$$L^1 = L_{z,z},$$

$$L^2 = L_{y,z} + L_{z,y},$$

$$L^3 = L_{x,z} + L_{y,y} + L_{z,x},$$

$$L^4 = L_{x,y} + L_{y,x},$$

$$L^5 = L_{x,x}.$$

The formal asymptotic solution of (1)-(2) is sought in the form

$$T^\varepsilon(\mathbf{x}) = T_0(\mathbf{x}, \mathbf{y}, \mathbf{z}) + \varepsilon T_1(\mathbf{x}, \mathbf{y}, \mathbf{z}) + \varepsilon^2 T_2(\mathbf{x}, \mathbf{y}, \mathbf{z}) + \varepsilon^3 T_3(\mathbf{x}, \mathbf{y}, \mathbf{z}) + \varepsilon^4 T_4(\mathbf{x}, \mathbf{y}, \mathbf{z}) + \dots, \quad (5)$$

where T_i are differentiable functions, and Y -periodic with respect to $\mathbf{y}$ and Z -periodic with respect to $\mathbf{z}$. The operator $\partial/\partial x_i$ for a function $v = \hat{v}(\mathbf{x}) = \tilde{v}(\mathbf{x}, \mathbf{y}, \mathbf{z})$ is thus determined using the chain rule,

$$\frac{\partial v}{\partial x_i} = \frac{\partial \hat{v}}{\partial x_i} = \frac{\partial \tilde{v}}{\partial x_i} + \frac{\partial \tilde{v}}{\partial y_i} \frac{\partial y_i}{\partial x_i} + \frac{\partial \tilde{v}}{\partial z_i} \frac{\partial z_i}{\partial x_i}, \quad (6)$$

such that

$$\frac{\partial}{\partial x_i} = \frac{\partial}{\partial x_i} + \frac{1}{\varepsilon} \frac{\partial}{\partial y_i} + \frac{1}{\varepsilon^2} \frac{\partial}{\partial z_i}. \quad (7)$$

Applying Eq. (7) to the left-hand side of Eq. (1) yields

$$\frac{\partial}{\partial x_i} \left(k_{ij}^\varepsilon \frac{\partial T^\varepsilon}{\partial x_j} \right) = \left(\frac{\partial}{\partial x_i} + \frac{1}{\varepsilon} \frac{\partial}{\partial y_i} + \frac{1}{\varepsilon^2} \frac{\partial}{\partial z_i} \right) \left(k_{ij}^\varepsilon \left(\frac{\partial T^\varepsilon}{\partial x_j} + \frac{1}{\varepsilon} \frac{\partial T^\varepsilon}{\partial y_j} + \frac{1}{\varepsilon^2} \frac{\partial T^\varepsilon}{\partial z_j} \right) \right), \quad (8)$$

or, equivalently,

$$\frac{\partial}{\partial x_i} \left(k_{ij}^\varepsilon \frac{\partial T^\varepsilon}{\partial x_j} \right) = \varepsilon^{-4} L^1 T^\varepsilon + \varepsilon^{-3} L^2 T^\varepsilon + \varepsilon^{-2} L^3 T^\varepsilon + \varepsilon^{-1} L^4 T^\varepsilon + \varepsilon^0 L^5 T^\varepsilon. \quad (9)$$

Using Eq. (9), Eq. (1) becomes

$$(\varepsilon^{-4} L^1 + \varepsilon^{-3} L^2 + \varepsilon^{-2} L^3 + \varepsilon^{-1} L^4 + \varepsilon^0 L^5) T^\varepsilon = f, \quad \text{in } \Omega. \quad (10)$$

Substituting the asymptotic expansion of T^ε up to ε^4 , Eq. (5), into Eq. (10), one obtains

$$(\varepsilon^{-4} L^1 + \varepsilon^{-3} L^2 + \varepsilon^{-2} L^3 + \varepsilon^{-1} L^4 + \varepsilon^0 L^5)(T_0 + \varepsilon T_1 + \varepsilon^2 T_2 + \varepsilon^3 T_3 + \varepsilon^4 T_4) = f, \quad \text{in } \Omega. \quad (11)$$

Equating to zero the terms corresponding to equal powers of ε , up to ε^0 , the following recurrent chain of equalities is obtained:

$$\text{from } \varepsilon^{-4}, \quad L^1 T_0 = 0, \quad (12)$$

$$\text{from } \varepsilon^{-3}, \quad L^1 T_1 = -L^2 T_0, \quad (13)$$

$$\text{from } \varepsilon^{-2}, \quad L^1 T_2 = -L^2 T_1 - L^3 T_0, \quad (14)$$

$$\text{from } \varepsilon^{-1}, \quad L^1 T_3 = -L^2 T_2 - L^3 T_1 - L^4 T_0, \quad (15)$$

$$\text{and from } \varepsilon^0, \quad L^1 T_4 = -L^2 T_3 - L^3 T_2 - L^4 T_1 - L^5 T_0 + f. \quad (16)$$

Note that all the equations (12)-(16) have a similar form,

$$L^1 U = F + \frac{\partial G_i}{\partial z_i}, \quad (17)$$

where L^1 involves $\mathbf{z}$ only, and U and G_i are Z -periodic. For Eq. (17), Bakhvalov and Panasenko (1989) proved that

$$\langle F \rangle_Z = 0 \quad (18)$$

is a necessary and sufficient condition for the existence of a periodic solution, and the latter is unique perhaps up to an additive constant. The angular brackets denote the average of the function F over the periodic cell Z ($|Z|^{-1} \int_Z F \, dz$).

By applying the solvability condition (18) to Eq. (12), one concludes that T_0 is a function of $\mathbf{x}$ and $\mathbf{y}$ only, or

$$T_0 = \tilde{T}_0(\mathbf{x}, \mathbf{y}). \quad (19)$$

Inserting Eq. (19) into Eq. (13), one obtains

$$L^1 T_1 = -\frac{\partial k_{ij}}{\partial z_i} \frac{\partial \tilde{T}_0}{\partial y_j}, \quad (20)$$

such that a solution to Eq. (20) can be represented as

$$T_1(\mathbf{x}, \mathbf{y}, \mathbf{z}) = -\chi_y^\ell(\mathbf{z}) \frac{\partial \tilde{T}_0}{\partial y_\ell}(\mathbf{x}, \mathbf{y}) + \tilde{T}_1(\mathbf{x}, \mathbf{y}), \quad (21)$$

where $\chi_y^\ell(\mathbf{z})$ is the solution of the local problem, or cell problem, described next.

First Local Problem. For each $\mathbf{y} \in Y$, find the parametric family of Z -periodic functions $\{\chi_y^j\}_{\mathbf{y} \in Y}$, such that

$$\Lambda_y^1(\chi_y^j - z_j) \equiv -\frac{\partial}{\partial z_i} \left(k_{ij} - k_{i\ell} \frac{\partial \chi_y^j}{\partial z_\ell} \right) = 0, \quad \text{in } Z \setminus \Gamma_y, \quad (22)$$

$$\langle \chi_y^j \rangle_Z = 0, \quad (23)$$

where Γ_y denotes the contact surfaces in Z for each $\mathbf{y} \in Y$.

With Eq. (19), Eq. (14) simplifies to

$$L^1 T_2 = -L_{z,y} T_1 - L_{y,z} T_1 - L_{z,x} \tilde{T}_0 - L_{y,y} \tilde{T}_0, \quad (24)$$

which, given Eq. (21), can be rewritten as

$$L^1 T_2 = -L_{z,y} T_1 - L_{z,x} \tilde{T}_0 - L_{y,y} \tilde{T}_0 + \frac{\partial}{\partial y_i} \left(k_{ij} \frac{\partial \chi_y^\ell}{\partial z_j} \frac{\partial \tilde{T}_0}{\partial y_\ell} \right). \quad (25)$$

From Eq. (18), the necessary and sufficient condition to be held for the solvability of Eq. (25) in the class of Z -periodic functions is

$$\left\langle -L_{y,y} \tilde{T}_0 + \frac{\partial}{\partial y_i} \left(k_{ij} \frac{\partial \chi_y^\ell}{\partial z_j} \frac{\partial \tilde{T}_0}{\partial y_\ell} \right) \right\rangle_Z = 0, \quad (26)$$

or, removing the y -derivatives and considering Eq. (19),

$$-\frac{\partial}{\partial y_i} \left\langle k_{i\ell} - k_{ij} \frac{\partial \chi_y^\ell}{\partial z_j} \right\rangle_Z \frac{\partial \tilde{T}_0}{\partial y_\ell} = 0. \quad (27)$$

Next, by introducing the operator

$$\Lambda^2 \equiv -\frac{\partial}{\partial y_i} \left(k_{ij}^1(\mathbf{y}) \frac{\partial}{\partial y_j} \right) \quad (28)$$

with

$$k_{ij}^1(\mathbf{y}) \equiv \left\langle k_{ij} - k_{i\ell} \frac{\partial \chi_y^j}{\partial z_\ell} \right\rangle_Z, \quad (29)$$

Eq. (27) takes the more compact form

$$\Lambda^2 \tilde{T}_0 = 0. \quad (30)$$

Eq. (30) constitutes the *intermediate homogenized problem*, whose effective thermal conductivity tensor is $k_{ij}^1(\mathbf{y})$. The tensor k_{ij}^1 preserves the symmetry and positive definiteness properties of k_{ij} .

Using a similar argument as that for the deduction of Eq. (19) from Eq. (12), one concludes from Eq. (30) that

$$\tilde{T}_0 = T(\mathbf{x}). \quad (31)$$

Substituting Eq. (31) into Eq. (21) for T_1 yields

$$T_1 = \tilde{T}_1(\mathbf{x}, \mathbf{y}). \quad (32)$$

Now substituting Eq. (31) and Eq. (32) into Eq. (25) yields

$$L^1 T_2 = -\frac{\partial k_{ij}(\mathbf{y}, \mathbf{z})}{\partial z_i} \left(\frac{\partial T}{\partial x_j} + \frac{\partial \tilde{T}_1}{\partial y_j} \right). \quad (33)$$

In analogy to Eqs. (20)-(21), a solution to Eq. (33) can be represented as

$$T_2(\mathbf{x}, \mathbf{y}, \mathbf{z}) = -\chi_y^\ell(\mathbf{z}) \left(\frac{\partial T(\mathbf{x})}{\partial x_\ell} + \frac{\partial \tilde{T}_1(\mathbf{x}, \mathbf{y})}{\partial y_\ell} \right) + \tilde{T}_2(\mathbf{x}, \mathbf{y}). \quad (34)$$

Considering Eq. (31) and Eq. (32), Eq. (15) transforms to

$$L^1 T_3 = -(L_{y,z} T_2 + L_{z,y} T_2 + L_{y,y} \tilde{T}_1 + L_{z,x} \tilde{T}_1 + L_{y,x} T). \quad (35)$$

Substituting into Eq. (35) the expression (34) for T_2 yields

$$\begin{aligned} L^1 T_3 = & \frac{\partial}{\partial y_i} \left(k_{ij} \frac{\partial \chi_y^\ell}{\partial z_j} \left(\frac{\partial T}{\partial x_\ell} + \frac{\partial \tilde{T}_1}{\partial y_\ell} \right) \right) - \frac{\partial}{\partial y_i} \left(k_{ij} \frac{\partial \tilde{T}_1}{\partial y_j} \right) - \frac{\partial}{\partial y_i} \left(k_{ij} \frac{\partial T}{\partial x_j} \right) \\ & - \frac{\partial}{\partial z_i} \left(-k_{ij} \chi_y^\ell \frac{\partial^2 \tilde{T}_1}{\partial y_j \partial y_\ell} + k_{ij} \frac{\partial \tilde{T}_2}{\partial y_j} + k_{ij} \frac{\partial \tilde{T}_1}{\partial x_j} \right). \end{aligned} \quad (36)$$

Applying once again the solvability condition (18) to Eq. (36), one obtains

$$\left\{ -\frac{\partial}{\partial y_i} \frac{1}{|Z|} \left(\int_Z k_{ij} dz - \int_Z k_{i\ell} \frac{\partial \chi_y^j}{\partial z_\ell} dz \right) \frac{\partial}{\partial y_j} \right\} \tilde{T}_1 = \frac{\partial T}{\partial x_j} \left\{ \frac{\partial}{\partial y_i} \frac{1}{|Z|} \left(\int_Z k_{ij} dz - \int_Z k_{i\ell} \frac{\partial \chi_y^j}{\partial z_\ell} dz \right) \frac{\partial}{\partial y_j} \right\} y_j. \quad (37)$$

Using the definition of the operator Λ^2 , Eq. (37) becomes

$$\Lambda^2 \tilde{T}_1 = -(\Lambda^2 y_j) \frac{\partial T}{\partial x_j}. \quad (38)$$

It is now possible to separate variables $\mathbf{x}$ and $\mathbf{y}$, and write $\tilde{T}_1$ as

$$\tilde{T}_1 = -\chi^j(\mathbf{y}) \frac{\partial T(\mathbf{x})}{\partial x_j} + \tilde{T}_1(\mathbf{x}). \quad (39)$$

The expression (34) for T_2 thus becomes

$$T_2 = -\chi_y^\ell(\mathbf{z}) \left(\frac{\partial T(\mathbf{x})}{\partial x_\ell} - \frac{\partial \chi^j(\mathbf{y})}{\partial y_\ell} \frac{\partial T(\mathbf{x})}{\partial x_j} \right) + \tilde{T}_2(\mathbf{x}, \mathbf{y}). \quad (40)$$

Substituting Eq. (39) into Eq. (38), one obtains the local problem, or cell problem, described next.

Second Local Problem. Find χ^j , Y -periodic, such that

$$\Lambda^2(\chi^j - y_j) = \frac{\partial}{\partial y_i} \left(k_{ij}^1 - k_{i\ell}^1 \frac{\partial \chi^j}{\partial y_\ell} \right) = 0, \quad \text{in } Y. \quad (41)$$

The solution χ^j can be determined up to an additive constant. Possible discontinuities of k_{ij}^1 are not considered here.

From Eq. (18), the necessary and sufficient condition for the existence of a Z -periodic solution of Eq. (16) is

$$\langle L_{y,z} T_3 + (L_{x,z} + L_{y,y}) T_2 + (L_{x,y} + L_{y,x}) T_1 + L_{x,x} T_0 \rangle_Z = f. \quad (42)$$

In view of Y -periodicity, on applying the average operator $\langle \cdot \rangle_Y$ to both sides of Eq. (42) one obtains

$$\langle \langle L_{x,z} T_2 + L_{x,y} T_1 + L_{x,x} T_0 \rangle_Z \rangle_Y = \langle f \rangle_Y = f. \quad (43)$$

Substituting the expressions (31), (39), and (40) for T_0 , T_1 , and T_2 , respectively, into Eq. (43), and doing the algebra straightforwardly, leads to the *homogenized problem*

$$\hat{k}_{ij} \frac{\partial^2 T}{\partial x_i \partial x_j} = f, \quad \text{in } \Omega, \quad (3)$$

whose components of the effective conductivity tensor are defined by

$$\hat{k}_{ij} = \left\langle \left(k_{ij} - k_{i\ell} \frac{\partial \chi_y^j}{\partial z_\ell} \right) - \left(k_{im} - k_{i\ell} \frac{\partial \chi_y^m}{\partial z_\ell} \right) \frac{\partial \chi^j}{\partial y_m} \right\rangle_{Y \times Z}. \quad (44)$$

Clearly, Eq. (44) can be rewritten as

$$\hat{k}_{ij} = \left\langle k_{ij}^1 - k_{im}^1 \frac{\partial \chi^j}{\partial y_m} \right\rangle_Y, \quad (45)$$

so that it incorporates the homogenization results from the previous level Z . It is worth noting that the effective tensor defined by (44) is symmetric and positive definite.

3. APPLICATION TO A FUNCTIONALLY GRADED MATERIAL

In this section the particular case of a periodic functionally graded material (FGM) is considered, whose coefficients $k_{ij}^\varepsilon(\mathbf{x}) = k_{ij}(\mathbf{y}, \mathbf{z})$ are rapidly oscillating, isotropic ($k_{ij}^\varepsilon(\mathbf{x}) = k^\varepsilon(\mathbf{x}) \delta_{ij} = k(\mathbf{y}, \mathbf{z}) \delta_{ij}$), infinitely differentiable ($k_{ij}^\varepsilon(\mathbf{x}) \in C^\infty(\Omega)$), and positive-definite ($\exists c > 0 \forall \boldsymbol{\eta} \in \mathbb{R}^3 : k_{ij} \eta_i \eta_j \geq c |\boldsymbol{\eta}|^2$, $\boldsymbol{\eta} = (\eta_1, \eta_2, \eta_3)$, $|\boldsymbol{\eta}|^2 = \sum_1^3 \eta_i^2$). Because the coefficients are infinitely differentiable, it is not necessary to impose contact conditions on the constituents interfaces.

The procedure of the previous section is here applied to a periodic FGM (Paulino *et al.*, 2009) with $k^\varepsilon(\mathbf{x}) = k(\mathbf{y}, \mathbf{z})$ being $Y \times Z \equiv [0, 1] \times [0, 1]$ -periodic and given, with respect to some reference conductivity, by the trigonometric function

$$k^\varepsilon(\mathbf{x}) = \begin{cases} 1 + 0.25 \sin \frac{2\pi x_1}{\varepsilon} \sin \frac{2\pi z_1}{\varepsilon^2}, & x_1 \in [(n-1)\varepsilon, (n-0.5)\varepsilon], \\ 1, & x_1 \in [(n-0.5)\varepsilon, n\varepsilon], \end{cases} \quad (46)$$

or

$$k(\mathbf{y}, \mathbf{z}) = \begin{cases} 1 + 0.25 \sin 2\pi y_1 \sin 2\pi z_1, & y_1 \in [(n-1), (n-0.5)], z_1 \in [(n-1)/\varepsilon, (n-0.5)/\varepsilon], \\ 1, & y_1 \in [(n-0.5), n], z_1 \in [(n-0.5)/\varepsilon, n/\varepsilon]. \end{cases} \quad (47)$$

It is considered that the small parameter ε takes values in the succession $\{1/n : n \in \mathbb{N}\}$, such that k^ε has periods ε and ε^2 . The local function is seen to depend on the fast variables $y \equiv y_1$ and $z \equiv z_1$ only. Figure 1 illustrates the rapidly oscillating character of the function $k^\varepsilon(\mathbf{x})$ for various values of ε . Figure 2 illustrates the functionally graded behavior of the conductivity $k(\mathbf{y}, \mathbf{z})$ by considering the periodic part $[0, 1] \times [0, 1]$ of its domain of definition. For the FGM characterized by Eq. (47), a one-dimensional homogenization problem is, therefore, obtained, whose periodic cell solutions of Eqs. (22) and (41) must be found, in order to calculate the effective conductivity tensor given by Eq. (45).

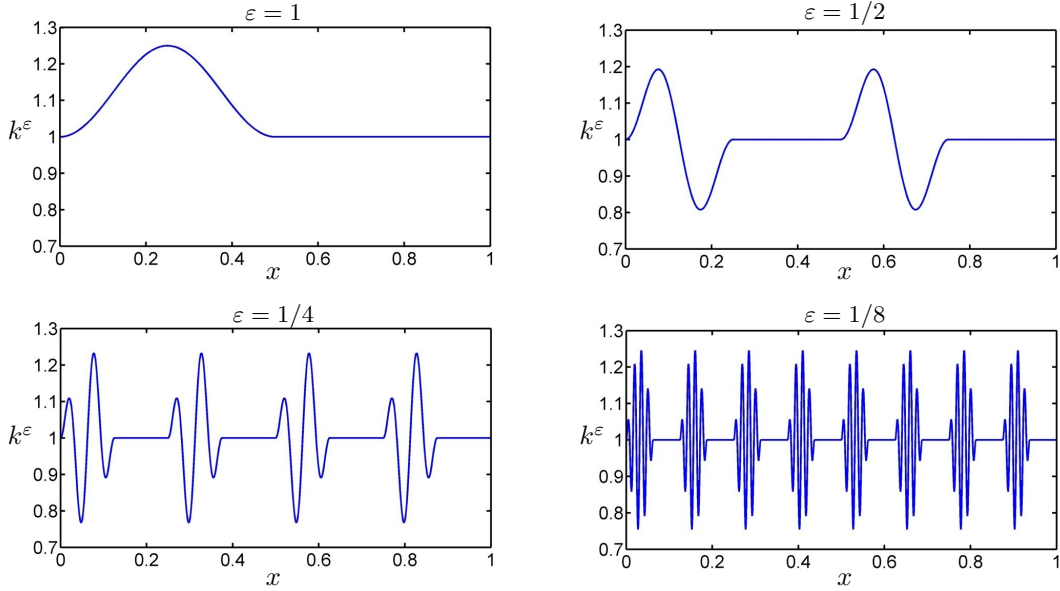


Figure 1. An illustration of the rapidly oscillating character of the function $k^\varepsilon(\mathbf{x})$ ($x \equiv x_1$).

First Local Problem. For each $\mathbf{y} \in Y$, find the parametric family of Z -periodic functions $\{\chi_y^j\}_{\mathbf{y} \in Y}$, such that

$$-\frac{d}{dz} \left(k_{1j} - k_{11} \frac{d\chi_y^j}{dz} \right) = 0, \quad \text{in } Z, \quad (48)$$

$$\chi_y^j(0) = \chi_y^j(1), \quad (49)$$

$$\langle \chi_y^j \rangle_Z = 0. \quad (50)$$

Integrating (48) in $z \in Z$, one obtains

$$k_{1j} - k_{11} \frac{d\chi_y^j}{dz} = C_j, \quad C_j \text{ const. } \forall j. \quad (51)$$

Thus

$$-k_{11} \frac{d\chi_y^j}{dz} = C_j - k_{1j}, \quad \text{or} \quad \frac{d\chi_y^j}{dz} = k_{11}^{-1} (k_{1j} - C_j). \quad (52)$$

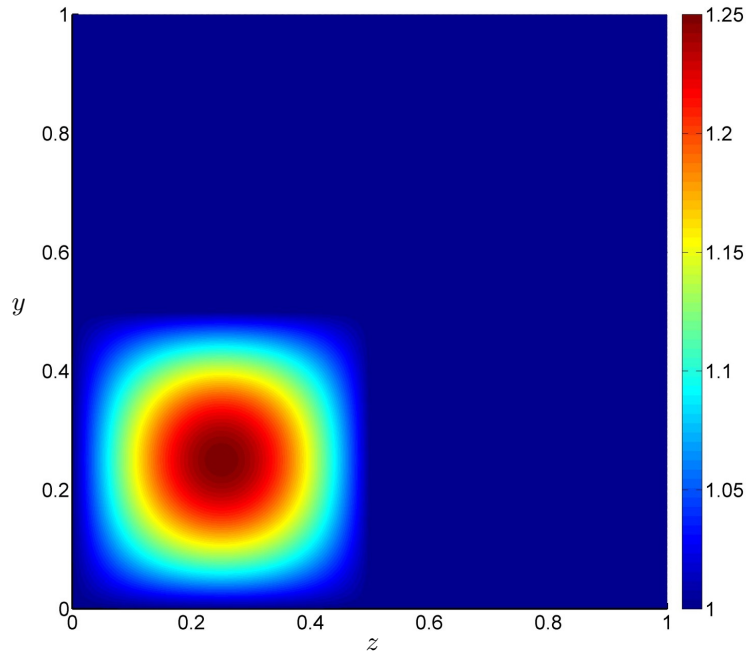


Figure 2. Periodic part ($n = 1$) of the domain of definition of the conductivity function $k(\mathbf{y}, \mathbf{z})$ of the FGM.

Integrating Eq. (52) from 0 to 1 yields

$$\int_0^1 \frac{d\chi_y^j}{dz} dz = \int_0^1 k_{11}^{-1} k_{1j} dz - C_j \int_0^1 k_{11}^{-1} dz. \quad (53)$$

Because $\chi_y^j(0) = \chi_y^j(1)$, Eq. (53) gives

$$0 = \langle k_{11}^{-1} k_{1j} \rangle_Z - C_j \langle k_{11}^{-1} \rangle_Z, \quad \text{or} \quad C_j = \langle k_{11}^{-1} \rangle_Z^{-1} \langle k_{11}^{-1} k_{1j} \rangle_Z. \quad (54)$$

Substituting Eq. (54) into Eq. (52) yields

$$\frac{d\chi_y^j}{dz} = k_{11}^{-1} k_{1j} - \langle k_{11}^{-1} \rangle_Z^{-1} \langle k_{11}^{-1} k_{1j} \rangle_Z, \quad (55)$$

so that Eq. (50) is satisfied.

With the solutions $\{\chi_y^j\}_{\mathbf{y} \in Y}$ of the First Local Problem, it is possible to calculate the effective coefficients

$$k_{ij}^1 = \left\langle k_{ij} - k_{i1} \frac{d\chi_y^j}{dz} \right\rangle_Z = \langle k_{ij} \rangle_Z - \left\langle k_{i1} \frac{d\chi_y^j}{dz} \right\rangle_Z. \quad (56)$$

As a matter of fact, substituting Eq. (55) into Eq. (56) one arrives at

$$k_{ij}^1 = \langle k_{ij} \rangle_Z - \langle k_{i1} k_{11}^{-1} k_{1j} \rangle_Z + \langle k_{i1} k_{11}^{-1} \rangle_Z \langle k_{11}^{-1} \rangle_Z^{-1} \langle k_{11}^{-1} k_{1j} \rangle_Z \quad (57)$$

One may verify that: (i) $k_{ij}^1 = k_{ij}^1(y) \in C^\infty$; (ii) $k_{ij}^1 = k_{ji}^1$; and (iii) $\exists c' > 0 \forall \boldsymbol{\eta} \in \mathbb{R}^3 : k_{ij}^1 \eta_i \eta_j \geq c' |\boldsymbol{\eta}|^2$.

Second Local Problem. Find χ^j , Y -periodic, such that

$$\frac{d}{dy} \left(k_{1j}^1 - k_{11}^1 \frac{d\chi^j}{dy} \right) = 0, \quad \text{in } Y, \quad (58)$$

$$\chi^j(0) = \chi^j(1). \quad (59)$$

The solution of this problem can be determined up to an additive constant.

The second local problem can be solved in a similar fashion, such that one can directly write

$$\hat{k}_{ij} = \langle k_{ij}^1 \rangle_Y - \langle k_{i1}^1 (k_{11}^1)^{-1} k_{1j}^1 \rangle_Y + \langle k_{i1}^1 (k_{11}^1)^{-1} \rangle_Y \langle (k_{11}^1)^{-1} \rangle_Y^{-1} \langle (k_{11}^1)^{-1} k_{1j}^1 \rangle_Y. \quad (60)$$

In particular, for the case being considered, $k_{ij}(\mathbf{y}, \mathbf{z}) = k(\mathbf{y}, \mathbf{z})\delta_{ij}$, and Eq. (57) yields

$$k_{ij}^1 = \langle k \rangle_Z \delta_{ij} - (\langle k \rangle_Z - \langle k^{-1} \rangle_Z^{-1}) \delta_{i1} \delta_{1j}. \quad (61)$$

As a consequence,

$$k_{11}^1 = \langle k^{-1} \rangle_Z^{-1}, \quad k_{22}^1 = k_{33}^1 = \langle k \rangle_Z, \quad k_{ij}^1 = 0 \text{ for } i \neq j. \quad (62)$$

Now with the help of a math code, on substituting Eq. (47) for k and Eq. (62) into the solution of the second local problem, Eq. (60), one finally determines the effective thermal conductivities,

$$\begin{aligned} \hat{k}_{11} &= \langle k_{11}^1 \rangle_Y - \langle k_{11}^1 (k_{11}^1)^{-1} k_{11}^1 \rangle_Y + \langle k_{11}^1 (k_{11}^1)^{-1} \rangle_Y \langle (k_{11}^1)^{-1} \rangle_Y^{-1} \langle (k_{11}^1)^{-1} k_{11}^1 \rangle_Y \\ &= \langle (k_{11}^1)^{-1} \rangle_Y^{-1} = \langle \langle k^{-1} \rangle_Z^{-1} \rangle_Y^{-1} \equiv \langle k^{-1} \rangle_{Y \times Z}^{-1} = (0.228 + 0.75)^{-1} = 1.0225, \end{aligned} \quad (63)$$

$$\hat{k}_{22} = \hat{k}_{33} = \langle k_{22}^1 \rangle_Y = \langle k \rangle_{Y \times Z} = 0.25 + \frac{0.25}{\pi^2} + 0.75 = 1.0253, \quad (64)$$

$$\hat{k}_{ij} = 0 \text{ for } i \neq j. \quad (65)$$

4. CONCLUSIONS

In the present work the strong-form Fourier heat conduction equation for heterogeneous media with multiple spatial scales has been successfully derived using the method of reiterated homogenization. The effective coefficients can be calculated by solving two local or cell problems, while the macroscopic behavior is governed by the homogenized problem. To facilitate the physical understanding of the technique, an analytical solution is obtained for the heat conduction equation in a trigonometric functionally graded material. The approach presented here shall serve as a basis for future efforts to numerically compute effective properties of more complex materials with multiple spatial scales.

5. ACKNOWLEDGEMENTS

Support provided by CNPq – Brazilian National Council for Scientific and Technological Development (projects nos. 303208/2014-7 and 451698/2015-0) and CAPES – Brazilian Coordination for the Improvement of Higher Education Personnel (project no. 88881.030424/2013-01) is gratefully acknowledged. M.E. Cruz and J.B. Castillero are thankful to the Mechanical Engineering Program/COPPE/UFRJ for travel support.

6. REFERENCES

- Allaire, G. and Briane, M., 1996. “Multiscale convergence and reiterated homogenisation”. *Proceedings of the Royal Society of Edinburgh: Section A Mathematics*, Vol. 126, No. 2, pp. 297-342.
- Bakhvalov, N. and Panasenko, G., 1989. *Homogenisation: Averaging Processes in Periodic Media*. Kluwer Academic Publishers, Dordrecht, The Netherlands.
- Bensoussan, A., Lions, J.-L. and Papanicolaou, G., 1978. *Asymptotic Analysis for Periodic Structures*. North-Holland Publishing Company, Amsterdam.
- Mahmood, R.M., Akinlabi, E.T., Shukla, M. and Pityana, S., 2012. “Functionally Graded Material: An Overview”. *Proceedings of the World Congress on Engineering - WCE 2012*, Vol. III. London, U.K.
- Panasenko, G.P., 2008. “Homogenization for Periodic Media: from Microscale to Macroscale”. *Physics of Atomic Nuclei*, Vol. 71, No. 4, pp. 681-694.
- Paulino, G.H., Silva, E.C.N. and Le, C.H., 2009. “Optimal design of periodic functionally graded composites with prescribed properties”. *Structural and Multidisciplinary Optimization*, Vol. 38, No. 5, pp. 469-489.
- Wagnier, H., Kromm, F.X., Danis, M. and Brechet, Y., 2014. “Proposal for a multi-material design procedure”. *Materials and Design*, Vol. 56, pp. 44-49.
- Yin, H.M., Paulino, G.H., Buttlar, W.G. and Sun, L.Z., 2005. “Effective thermal conductivity of two-phase functionally graded particulate composites”. *Journal of Applied Physics*, Vol. 98, No. 6, 063704.

7. RESPONSIBILITY NOTICE

The authors are the only responsible for the printed material included in this paper.